

TAILORED NANO-STRUCTURED COATINGS *via* LII-CONTROLLED FLAME SYNTHESIS FOLLOWED BY 'RESONANT IMPACTION'

NSF Functional Nanostructures Grant 9871885

D. E. Rosner(PI), J. Fernandez de la Mora, M.B. Long, and W. Tong

Yale University, Departments of Chemical and Mechanical Engineering; NSF Grant CTS-9871885

The premise of this pilot NSF program is that *aggregation* in high-yield flame synthesis nano-particle reactors is no impediment to ultimately forming useful (dense, nano-structured) coatings, so long as flame conditions are controlled to preclude strong inter-spherule bonds. We believe that this *can* be accomplished, and such “weakly bonded” aggregates can be gas-dynamically accelerated and broken up upon high velocity impact. Toward this end, our program has focused on obtaining the requisite fundamental understanding in 4 key areas, briefly summarized below:

1. Aggregation and Sintering in Well-Defined Inorganic Nano-Particle Synthesis Flames

(D.E. Rosner)

We have obtained, and are currently exploiting, a rather complete set of data on *alumina* nano-aggregate population evolution using a “seeded” counterflow laminar diffusion flame reactor with laser-based optical- as well as TEM grid thermophoretic sampling (Xing *et al.*, 1999). Currently, we are developing tractable simulation tools to predict this population evolution both using presently available rate/transport laws (for aggregate coagulation frequency, thermophoresis and sintering (in terms of the state variables: particle volume, v and surface area, a), as well as rational improvements, currently under development). Our bivariate simulation methods (Rosner and Pyykonen, 2001), the simplest of which is equivalent to a 9-moment method, will also lend itself to future parameter estimation; *eg.*, inferring a “best-fit” activation energy for alumina nano-particle sintering by, say, surface-diffusion (see, *eg.*, Xing and Rosner, 1999). Variants/extensions of these simulation techniques should also enable incorporation into, say, full *PDF*-methods for *turbulent* synthesis reactors of industrial interest.

2. Use of LII and LLS for Real-Time *In-situ* Suspended Nano-Aggregate Characterization (M. B. Long, A. Schaffer, A. Filippov and D.E. Rosner)

While angle-dependent “elastic” laser light scattering (LLS) provides local, *in situ* information on the state of nano-particle *aggregation* in well-defined flame environments (Xing, *et al.*, 1999), it is now clear that, when combined with *time-resolved laser-induced incandescence* (LII), it is also possible to obtain *spherule sizes* in atmospheric pressure flames. This has been demonstrated using 532 nm Nd-YAG pulses of *ca.* 8 ns duration to size absorbing spherules in the *ca.* 20 nm diam. range, provided the dispersity of the spherule population is sufficiently narrow (Schaffer *et al.*, 2001). Adequately narrow distributions of alumina spherules *have* been observed in our counterflow laminar diffusion flame experiments, but since alumina is only weakly absorbing at 532 nm, we have been optically and thermophoretically probing *iron oxide* nano-aggregates in flat premixed flames at temperatures below 1600K. In a promising recent development, it appears that it may not only be possible to do time-resolved LII spherule *sizing* at low laser fluences (say, below 0.02 J/cm²), but that there is simultaneous LLS-evidence for *laser-induced aggregate break-up* (LIABU) at somewhat higher laser fluences (but well below the apparent spherule vaporization threshold). These observations may provide us with an additional (on-line “optical”) way to characterize the apparent *interspherule bonding* in such flame-produced nano-aggregate structures (*cf.* Section 3, below). The

interpretation of further LIABU measurements will be initiated in the remaining 7 months of the present NSF program.

3. Threshold Conditions for Impact-Breakup of Well-defined Aggregates

(J. Fernandez de la Mora)

This task involves: (a) developing techniques to produce well-defined aggregates, (b) studying their collision against a surface at controlled velocities, and (c) EM analysis of the impact products. Task (a) has been completed. Available mono-disperse nano-spheres of a desired material are suspended in a highly conducting liquid and electro-sprayed into drops of predetermined size, containing 1, 2,..., n, suspended spheres. The liquid and salt in the drops evaporates, leaving compact aggregates. While the *spherule* diameter is thereby fixed, spraying produces a distribution of *cluster* sizes. Figure 1a shows a DMA-derived *mobility distribution* of such clusters. Since multiple charges have been eliminated by neutralization, the measured mobility is simply related to aggregate size, with the left-most peak corresponding to one sphere (here the protein lysozyme), etc., so that the n^{th} peak is known unambiguously to contain n primary spheres (or globules). While individual peaks cannot be distinguished beyond *ca.* $n=12$ (due to the finite size-spread of the starting spheres) a simple relation between aggregate mobility and n (*cf* Fig 1b) allows selecting larger clusters with known n-values (with essentially no upper limit). This procedure applies to other proteins, with molecular masses, M, from 14 to 44 kDa, and other materials, including: chain polymers (*eg.*, poly-ethylene glycol ($4 < M < 120$ kDa), and multi-branched spheroidal polymers ("dendrimers"; $3.3 < M < 28$ kDa). We will investigate as many sphere types as monodisperse samples become available.

Task (b) is currently being carried out using a *hypersonic impactor*. Here the jet formed by expansion of a carrier gas accelerates the mobility-selected aggregates, whose impact velocity can be controlled up to *ca.* 1 km/s. A new impactor was installed/calibrated in Fall 2000 for diameters down to 16 nm. We are currently extending the calibration down to *ca.* 4 nm, and will start impacting some of the clusters described. Our first candidates will be dendrimers (with intra-sphere bonds much stronger than the interspherule forces).

4. Characterization of "Nanostructured Coatings" (C. Xie (GRA) and W. Tong)

This task is concerned with developing new methodologies to characterize nano-scale film coatings, including fracture strength and strength of the coating-substrate interface. A reliable and consistent measurement of these properties is critical to control/improve thin film coating processing technologies. Essential aspects of our methodology include (a) *in-situ* tensile testing of plastically deformed coated substrate under an optical microscope, SEM and AFM, and (b) a nonlinear finite-element analysis of such coating-substrate systems. As an illustration, we have successfully studied nano-scale anodic oxide coatings (10-300 nm) on aluminum alloy substrates, with results presented at the *Int. Conf. Metallurgical Coatings and Thin Films* (April 10-14, 2000, San Diego, CA) and the *SEM IX Int. Congress Exp. Mechanics* (June 5-8, 2000, Orlando, FL). A paper: "Fracture of Nanostructured Thin Film Coatings" is being prepared for *Acta Materialia*. This sub-Task includes developing experimental capabilities for characterization, internal stress measurement, and annealing of nano-particle- and nano-structured coatings. With the help of two NSF equipment grants we have added to our materials research lab: (a) a Phillips XL30 SEM with energy dispersive chemical analysis (EDS), crystal orientation imaging microscopy (OIM) and micro-tensile test capabilities; and (b) dual X-ray diffractometers (Shimadzu XRD-6000, and Bede D1). A preliminary study of the effects of annealing of initially amorphous nano-scale oxide films on a Si substrate on their crystallization kinetics is currently underway.

References Cited

Filippov, A.V., Zurita, M. and Rosner, D. E., "Fractal-like Aggregates: Relation Between Morphology and Physical Properties", *J. Colloid Interface Sci.*, **229**, 261-273 (Sept. 2000); see, also: "Drag and Torque on Clusters of N Arbitrary Spheres at Low Reynolds Number", *ibid.*, **229**, 184-195 (Sept., 2000)

Fernández de la Mora, J., de Juan, L., Eichler, T. and Rosell, J. "Differential Mobility Analysis of Molecular Ions and Nanometer Particles", *Trends in Anal. Chem.*, **17**, 328-339, (1998)

Fernández de la Mora, J., Hering, S.V., Rao, N. and McMurry, P. "Hypersonic Impaction of Ultrafine particles", *J. Aerosol Sci.*, **21**, 169-187 (1990).


Gamero-Castaño, M. and Fernández de la Mora, J. "Mechanisms of electrospray ionization of singly and Multiply Charged Salt Clusters", *Analytica Chimica Acta*, **406**, 67-91, (2000)

Rosner, D.E. and Pyykonen, J.J., "Bi-variate Moment Method Simulation and Measurement of Populations of Coagulating and Sintering Nano-particles in Laminar Diffusion Flames", *AIChE J.* (to be submitted, Feb.2001; see, also: Rosner, D.E., *et al.*: "Relevant 'Mixed'-Moments for the Calculation of Deposition, Vapor Scavenging, and Optical Properties for Populations of Non-spherical Suspended Particles", Paper #10g in *Proc. AIChE 2000/Fourth Internat. Particle Technology Forum*, (CD format), November 2000

Rosner, D.E.: *Transport Processes in Chemically Reacting Flow Systems*, Dover Publications, Mineola NY, September 2000; ISBN/Dover # 0-486-41182-6

Schaffer, A., Long, M.B., Filippov, A.V. and Rosner D.E., "Nano-particle Sizing in Atmospheric Pressure Flames Using Time-Resolved LII", (in preparation, Feb. 2001)

Xing, Y., U.O. Köylü, and D.E. Rosner. "In situ Light-Scattering Measurements of Morphologically Evolving Flame-synthesized Oxide Nano-aggregates", *Applied Optics* **38**, 2686-2697 (1999); see, also: Xing, Y. and D.E. Rosner, "Prediction of Spherule Size in Gas Phase Nanoparticle Synthesis". *J. Nanoparticle Res.* **1**, 1-15 (1999)

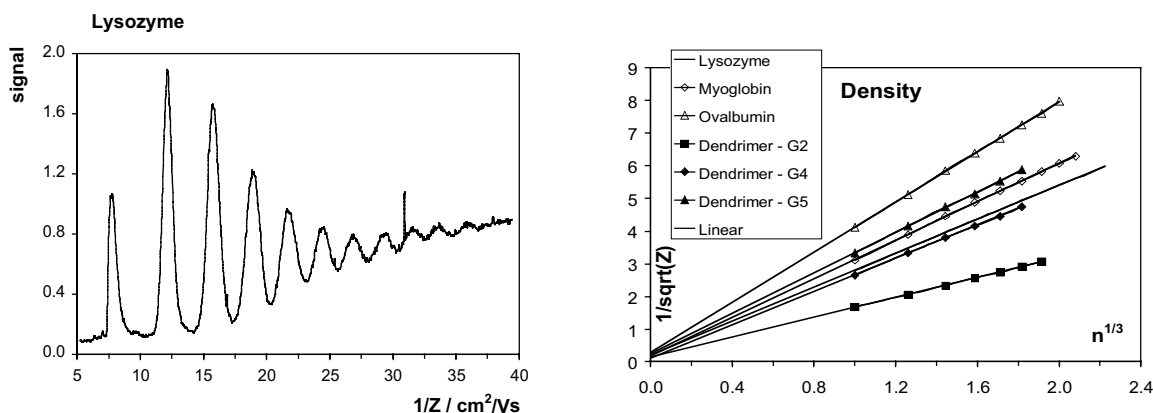

Part 2; Figure 1: Mobility spectra of aggregates from 1 to 12 lysozyme globules (left), and relation between mobility and degree n of clustering for the various aggregate types investigated (right).

Prepared for *Proc. Jan 29-30, 2001 NSF Nanotech Grantee Conference: 'Partnership in Nanotechnology'* (Arlington, VA)